



Recovery of Sodium Sulphate from Effluent Generated from Zeolite Y synthesis

Kabiru Musa Aujara ^{1*}, Abubakar Ali Ibrahim ¹, Abdulkarim Salawu Ahmed², Olusegun Ayoola Ajayi², Ibrahim Abubakar ¹ and Abdulkadir Abdulmalik ³

¹Department of Science Laboratory Technology, Collage of Science and Technology, Jigawa State Polytechnic, Dutse, Nigeria

²Department of Chemical Engineering, Ahmadu Bello University, Zaria, Nigeria

³Department of Chemistry, Rabi'u Musa Kwankwaso Collage of Advance and Remedial Studies, Tudun Wada, Kano State, Nigeria

Email address:

*Corresponding author: kbaujara@gmail.com

To cite this article:

Aujara, K.M., Ibrahim, A.A, Ahmed, A.S., Ajayi, O.A., Abubakar. I., Abdulmalik, A. Recovery of Sodium Sulphate from Effluent Generated from Zeolite Y synthesis. *International Journal of Research and Technopreneurial Innovations* 2024; 1(1): 78-84.

Keywords:

Nanofiltration, Zeolite, Membrane, Effluent, pH equalization

ABSTRACT



Zeolite production starting from raw kaolin is water intensive process. The process consists of six basic steps: Beneficiation of the raw kaolin, Calcination of beneficiated kaolin to produce metakaolin, dealumination of metakaolin to separate silica from alum, production of aluminum hydroxide from the alum, production of sodium silicate and production of zeolite. In this work, microfiltration, pH equalization and Nanofiltration (NF) were employed in the treatment of the effluent generated in the zeolite plant. Using NF3012 membrane element, the sodium sulphate solution in the effluent was concentrated and collected as retentate and also fresh water (permeate) was generated for reuse in the process. The concentrated solution was further crystallized by evaporation to produce anhydrous sodium sulphate. About 69.6 % of the wastewater recovered as permeate of the NF, and its quality is within the Nigerian industrial standard of water quality. High purity sodium sulphate was also recovered in form of thernadite, based on XRD and XRF results it is 98.1 % thernadite other solids impurities constituted of 1.9 %. The incorporation of microfiltration in the treatment process contributed a lot in improving the product quality in addition to minimizing the tendency of NF membrane fouling. The treatment of the effluents reduces their negative effects on human and the environment. It also generates fresh water and sodium sulphate for reuse. This could contribute towards achieving the objective of sustainable consumption of minerals and water.

1. INTRODUCTION

Zeolites are micro and mesoporous hydrated aluminosilicates of alkali elements, alkaline earth

metals, or other cations [1]. Their structure is built up with a framework of tetrahedral molecules, linked with shared oxygen atoms [2]. Zeolites are

commonly use as commercial adsorbents and catalysts. Zeolite production is increasing due to its wide application so also the effluent generated from it is becoming more and more significant [3,4]. (Barbosa et al., 2019). Raw kaolin is the starting raw material for the production of zeolite in the pilot plant in which this research was conducted [5,6]. The process involves six basic steps: Beneficiation of the raw kaolin, Calcination of beneficiated kaolin to produce metakaolin [3,7], dealumination of metakaolin to separate silica from alum, production of aluminium hydroxide from the alum, production of sodium silicate and production of zeolite [8,9]. In each of the above steps except in the calcination step a lot of wastewater is being generated [10,11]. Based on the material balance carried out in the pilot plant, processing of 2.5kg of metakaolin could generate as much as 10.4kg of sodium sulphate in waste water stream [12,13]. This is because excess sulphuric acid is being used to achieved complete dealumination (equation 1). Equation 2 and 3 show the two sources of the sodium sulphate as byproduct of the aluminum hydroxide production and the neutralization of the excess sulphuric acid respectively [14,15].



The excess sulphuric acid (H_2SO_4) in equation (1) was neutralized with sodium hydroxide (NaOH) to produce more sodium sulphate equation (3).



The world faces an ever-increasing freshwater scarcity and awareness of environmental deterioration; thus, the industries' wastewater must be treated, recycled, and reused [5,15,16].

Sodium sulphate which is major dissolved

substance in the waste is non-biodegradable and sometimes hazardous in nature [14,17]. It is most dangerous in structure conservation. When it grows in the pores of stones it can create high levels of pressure resulting in cracks within structures [10,18]. Its effects on human health is of relatively short-term and it is acute diarrhea, hence a substantial decrease of sulphate content in drinking water is recommendable [19,20]. Evaporation crystallization technology can transform these high-salt wastewater into solid crystal salt by thermal evaporation but becomes uneconomic at low concentration [21,22]. Membrane based separation processes have gradually proved an attractive alternative to the conventional separation processes for treatment of wastewater by pre-concentration of the feed [23]. They are gaining popularity in seawater desalination pre-treatment and water softening [18]. The application of membrane filtration not only enables high removal efficiencies, but also produce high quality water for reuse [24,25]. The separation of sodium sulphate salts from its aqueous solution has been studied by many researchers [26-28]. It is reported in the literature that performance of membrane depends on membrane characteristics (charge, pore size distribution etc.) [29], feed solution characteristics (pH, concentration etc.) [30] and system operating parameters (pressure, temperature etc.) [31].

In this work, Microfiltration, was employed to remove solid particles while Nanofiltration was used to concentrate the dissolved sodium sulphate while generating fresh water for reuse in the process. Sodium sulphate is a valuable material used in various industries for cleaning detergents, glass, pulp and paper. The aim of the work is to simultaneously recover sodium sulphate from zeolite pilot plant effluent and to generate fresh water for reuse.

2. MATERIALS AND METHODS

2.1. Membrane

In this work, Microfiltration, was employed to remove solid particles while Nanofiltration was used to concentrate the dissolved sodium sulphate while generating fresh water for reuse in the process. Sodium sulphate is a valuable material used in various industries for cleaning detergents, glass, pulp and paper. The aim of the work is to simultaneously recover sodium sulphate from zeolite pilot plant effluent and to generate fresh water for reuse.

2.2 Chemicals

Laboratory grade chemicals/reagents 98 wt% Concentrated sulphuric acid, 98 wt% Sodium hydroxide pellet manufactured by Loba chemie, Sodium sulphate manufactured by Thermo Fisher Scientific India Pvt. Ltd ≥ 99 wt% and distilled water were used in this study.

Table 1. Properties of membrane used.

S/N	Particulars	
1	Model	NF3012
2	Membrane active area (ft ² (m ²))	14.7 (1.37)
3	Membrane surface charge	Negative
4	Permeate flow rate GPD (m ³ /day)	350 (1.32)
5	Operating pH range	3.0 ~ 10.0
6	Max. Working pressure	300psi(2.07Mpa)
7	Operating temperature	45° C, Max.

Stable rejection for polyvalent salt >96% and 30%-50% for monovalent salt, recovery rate 15%

2.3 Feed, Permeate and Retentate analysis

Palintest made turbidity meter plus (model 1100), pH meter, conductivity meter and photometer (model 7100) were used in determination of turbidity/total suspended solids, pH, conductivity and concentration of sodium sulphate Na₂SO₄ in permeate and retentate.

2.4 Experimental set up

As shown in Figure 2, the raw water in the feed tank was pumped using 0.5hp booster through a microfilter element where associated solid particles were removed. The output of the microfilter was pumped using 0.5hp booster operating at 190psia through two stage Nanofiltration unit (NF3012). The permeate was collected in the treated water tank and taken for analysis while the retentate was collected in a separate container for further processing.

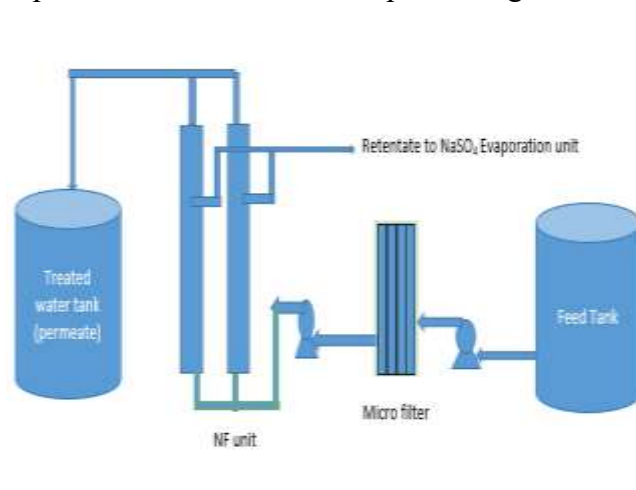


Figure 2. Effluent treatment steps

2.5 Evaporative Crystallization

250 ml of the retentate solution dried in an oven at 110°C for 24hrs until all the solvent (water) was evaporated. The dried crystals were then removed, labeled and kept in a clean container for further analysis.

2.6 Solid phase analysis

Mineralogical analysis of the product obtained from the drying of the retentate was performed by X-ray diffraction (XRD) using a ThermoScientific serial number 197492086 Model: ARL X'TRA X-ray diffractometer, ($\lambda = 1.540562$ Å; scanning speed $5^\circ/2\theta$ for the ranges $5-70^\circ 2\theta$) and the XRF was done using Minipal 4, Pananalytical X-ray fluorescence analyzer.

3. RESULTS AND DISCUSSION

3.1 Nanofiltration

The concentration of sodium sulphate in the feed of the nanofiltration unit was 4353.33 mg/l but after the filtration the permeate was found to consist of only 187 mg/l of the sodium sulphate (4.3% of the feed concentration). The pH, turbidity, TSS and the sodium sulphate

concentration of the permeate were all within the standard for drinking water quality in Nigeria as shown in Table 4. Moreover, the amount of fresh water recovered was 69.6% of the total feed water (Table 3). Since Nanofiltration removes all bacteria, and viruses hence the permeate is safe for drinking and reuse in the process [32]. Sodium sulphate rejection was found to be 95.7%.

Table 3. Properties of the treated water using nanofiltration.

Parameter	Feed	Permeate	Retentate	Efficiency (%)
pH	7.28	7.05	7.31	3.16 (pH reduction)
Turbidity (NTU)	0.42	0.14	0.52	66.67 (reduction in turbidity)
Conductivity ($\mu\text{S}/\text{cm}$)	7120	289	97895	95.94 (reduction in conductivity)
Na_2SO_4 (mg/l)	4353.33	187.07	13873.33	95.70 (Na_2SO_4 removal)
Volume (ltr)	25.00	17.40	7.60	69.60 (fresh water recovery)

Table 4: Comparison between the treated water and Nigerian Industrial Standard (NIS) for drinking water quality.

Parameters	Recovered fresh water (Permeate)	NIS
pH	7.05	6.5-8.5
Turbidity (NTU)	0.14	5
TSS (mg/l)	ND	NS
Na_2SO_4 (mg/l)	187	300

NIS: Nigerian industrial standard, NS: Not stated, ND: Not detected.

3.2 Product analysis.

The XRD (Fig.3) and XRF (Table 4) of the recovered sodium sulphate (product B) shows that high quality sodium sulphate (98.1 wt %) was recovered from the plant with very low incorporation of impurities (1.9 wt %). The XRD

results also determined the density of the product as $2.66\text{g}/\text{cm}^3$ and orthorhombic in shape. This is also comparable with commercial grade sodium sulphate [33].

SS: Sodium Sulphate

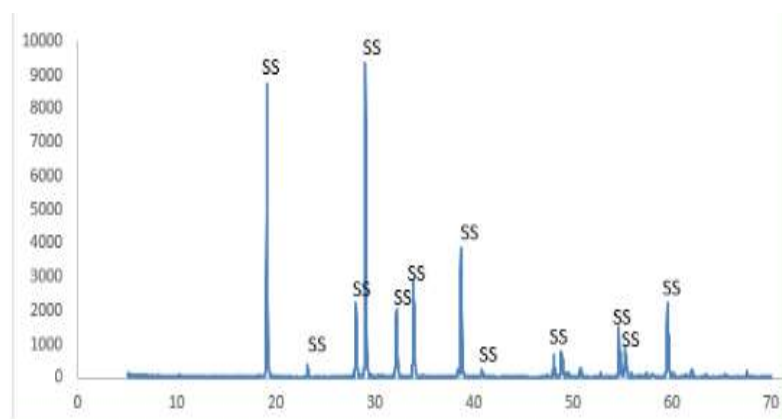


Figure 3: XRD pattern of the recovered products.

Table 4.8: XRF results for the recovered product.

Compound	SiO ₂	SO ₃	K ₂ O	Na ₂ O	Others
Product A (wt %)	1.5	55.2	0.1	42.8	0.3

4. CONCLUSION

Nanofiltration was successfully utilized to treat wastewater containing sodium sulphate and recovered 69.6% clean water (permeate) containing only 187 mg/l of sodium sulphate which was below the NIS maximum allowable limit (300 mg/l) for reuse.

Sodium sulphate of good quality (up to 98% as determined using XRD and XRF) was recovered from the wastewater by pre-concentration using Nanofiltration membrane followed by evaporative crystallization.

To achieved successful nanofiltration of wastewater that's results in purified water suitable for reuse or safe discharge, the following recommendation should be employed. Continues monitoring of key parameters such as pressure drop, permeate quality and fouling indicators. Proper management and dispose of the concentrate.

References

- [1] W. Shen and B. Shen, "Synthesis and characterization of composite structure zeolite Y," *Adv. Mater. Res.*, vol. 233–235, no. 1, pp. 1790–1793, 2011, doi: 10.4028/www.scientific.net/AMR.233-235.1790.
- [2] M. Wdowin and L. Bandura, "Erratum : The conversion technology of fly ash into zeolites (Clean Techn," vol. 16, no. March, pp. 2014–2015, 2015, doi: 10.1007/s10098-014-0719-6.
- [3] A. S. Barbosa, A. S. Barbosa, and M. G. F. Rodrigues, "Y-type zeolite membranes: Synthesis by secondary by method and application in treatment of oily effluents," *Mater. Sci. Forum*, vol. 958 MSF, pp. 23–28, 2019, doi: 10.4028/www.scientific.net/MSF.958.23.
- [4] A. Alkhoulzaam and H. Qiblawey, "Chemosphere Functional GO-based membranes for water treatment and desalination : Fabrication methods , performance and advantages . A review," *Chemosphere*, vol. 274, p. 129853, 2021, doi: 10.1016/j.chemosphere.2021.129853.
- [5] H. Faghihian and N. Godazandeha, "Synthesis of nano crystalline zeolite Y from bentonite," *J. Porous Mater.*, vol. 16, no. 3, pp. 331–335, 2009, doi: 10.1007/s10934-008-9204-0.
- [6] S. F. Anis, B. S. Lalia, R. Hashaikh, and N.

- Hilal, "Breaking through the selectivity-permeability tradeoff using nano zeolite-Y for micellar enhanced ultrafiltration dye rejection application," *Sep. Purif. Technol.*, vol. 242, p. 116824, 2020, doi: 10.1016/j.seppur.2020.116824.
- [7] M. U. Abba *et al.*, "Novel PVDF-PVP Hollow Fiber Membrane Augmented with TiO₂ Nanoparticles: Preparation, Characterization and Application for Copper Removal from Leachate," pp. 1–17, 2021.
- [8] N. Salahudeen and A. S. Ahmed, "Synthesis of hexagonal zeolite Y from Kankara kaolin using a split technique," *J. Incl. Phenom. Macrocycl. Chem.*, vol. 87, no. 1–2, pp. 149–156, 2017, doi: 10.1007/s10847-016-0686-0.
- [9] H. Sanaeepur, A. Kargari, and B. Nasernejad, "Aminosilane-functionalization of a nanoporous Y-type zeolite for application in a cellulose acetate based mixed matrix membrane for CO₂ separation," *RSC Adv.*, vol. 4, no. 109, pp. 63966–63976, 2014, doi: 10.1039/c4ra08783f.
- [10] R. Mahdavi Far, B. Van der Bruggen, A. Verliefde, and E. Cornelissen, "A review of zeolite materials used in membranes for water purification: history, applications, challenges and future trends," *J. Chem. Technol. Biotechnol.*, vol. 97, no. 3, pp. 575–596, 2022, doi: 10.1002/jctb.6963.
- [11] S. P. Solutions *et al.*, "Applications of micro size anorganic membrane of clay, zeolite and active carbon as filters for peat water purification Applications of micro size anorganic membrane of clay, zeolite and active carbon as filters for peat water purification," doi: 10.1088/1742-6596/1450/1/012010.
- [12] S. Bawa, A. Ahmed, P. Okonkwo, and S. Waziri, "DEVELOPMENT OF PILOT SCALE DEALUMINATION UNIT OF 2.5 kg METAKAOLIN PER BATCH CAPACITY," *Niger. J. Technol.*, vol. 36, no. 3, pp. 829–834, 2017, doi: 10.4314/njt.v36i3.24.
- [13] G. Clet, J. C. Jansen, and H. Van Bekkum, "Synthesis of a zeolite Y coating on stainless steel support," *Chem. Mater.*, vol. 11, no. 7, pp. 1696–1702, 1999, doi: 10.1021/cm980751o.
- [14] L. Bonaccorsi, L. Calabrese, and E. Proverbio, "Low temperature single-step synthesis of zeolite y coatings on aluminium substrates," *Microporous Mesoporous Mater.*, vol. 144, no. 1–3, pp. 40–45, 2011, doi: 10.1016/j.micromeso.2011.04.014.
- [15] Y. Shi, X. Meng, L. Yao, and M. Tian, "A full-scale study of nanofiltration: Separation and recovery of NaCl and Na₂SO₄ from coal chemical industry wastewater," *Desalination*, vol. 517, no. March, p. 115239, 2021, doi: 10.1016/j.desal.2021.115239.
- [16] W. Li, B. Van Der Bruggen, and P. Luis, "Chemical Engineering Research and Design Recovery of Na₂CO₃ and Na₂SO₄ from mixed solutions by membrane crystallization," *Chem. Eng. Res. Des.*, vol. 106, pp. 315–326, 2015, doi: 10.1016/j.cherd.2015.12.022.
- [17] C. Berger, R. Gläser, R. A. Rakoczy, and J. Weitkamp, "The synthesis of large crystals of zeolite y re-visited," *Microporous Mesoporous Mater.*, vol. 83, no. 1–3, pp. 333–344, 2005, doi: 10.1016/j.micromeso.2005.04.009.
- [18] N. Muhamad, N. Abdullah, M. A. Rahman, K. H. Abas, and A. A. Aziz, "Removal of nickel from aqueous solution using supported zeolite-Y hollow fiber membranes," 2018.
- [19] R. S. Gawaad, S. K. Sharma, and S. S. Sambhi, "Sodium Sulphate Recovery from Industrial Wastewater Using Nano-Membranes: a Review," vol. 3, no. May, pp. 392–398, 2011.
- [20] S. Mohammed, H. Nassrullah, J. Aburabie, and R. Hashaikeh, "Fabrication of Thin Film Composite Membranes on Nanozeolite Modified Support Layer for Tailored Nanofiltration Performance," 2022.
- [21] "Critical Review The Global Rise of Zero Liquid Discharge for Wastewater Management: Drivers, Technologies," 2016, doi: 10.1021/acs.est.6b01000.
- [22] H. C. Man, M. U. Abba, M. Abdulsalam, S. Azis, A. I. Idris, and M. H. Hamzah, "Utilization of Nano-TiO₂ as an Influential Additive for Complementing Separation Performance of a Hybrid PVDF-PVP

- Hollow Fiber: Boron Removal from Leachate,” 2020.
- [23] D. Wu, Y. Han, L. Zhao, W. Salim, V. Vakharia, and W. S. W. Ho, “Scale-up of zeolite-Y/polyethersulfone substrate for composite membrane fabrication in CO₂ separation,” *J. Memb. Sci.*, vol. 562, no. May, pp. 56–66, 2018, doi: 10.1016/j.memsci.2018.05.021.
- [24] S. Yousef, S. Tuckute, A. Tonkonogovas, and A. Mohamed, “Ultra-permeable CNTs / PES membranes with a very low CNTs content and high H₂ / N₂ and CH₄ / N₂ selectivity for clean energy extraction applications,” 2021, doi: 10.1016/j.jmrt.2021.10.125.
- [25] N. Taufiqurrahmi, A. R. Mohamed, and S. Bhatia, “Nanocrystalline zeolite Y: Synthesis and characterization,” *IOP Conf. Ser. Mater. Sci. Eng.*, vol. 17, no. 1, 2011, doi: 10.1088/1757-899X/17/1/012030.
- [26] Z. Traps, “Zeolite membranes for chemical separation Behind the Research,” doi: 10.1021/acsami.8b20151.
- [27] L. Qin *et al.*, “Oriented Clay Nanotube Membrane Assembled on Microporous Polymeric Substrates,” 2016, doi: 10.1021/acsami.6b12858.
- [28] Y. Mu, K. Zhu, J. Luan, S. Zhang, C. Zhang, and R. Na, “Fabrication of hybrid ultra filtration membranes with improved water separation properties by incorporating environmentally friendly taurine modified hydroxyapatite nanotubes,” *J. Memb. Sci.*, vol. 577, no. January, pp. 274–284, 2019, doi: 10.1016/j.memsci.2019.01.043.
- [29] H. Wu, B. Zheng, X. Zheng, J. Wang, W. Yuan, and Z. Jiang, “Surface-modified Y zeolite-filled chitosan membrane for direct methanol fuel cell,” *J. Power Sources*, vol. 173, no. 2 SPEC. ISS., pp. 842–852, 2007, doi: 10.1016/j.jpowsour.2007.08.020.
- [30] K. Ramasubramanian, M. A. Severance, P. K. Dutta, and W. S. W. Ho, “Fabrication of zeolite/polymer multilayer composite membranes for carbon dioxide capture: Deposition of zeolite particles on polymer supports,” *J. Colloid Interface Sci.*, vol. 452, pp. 203–214, 2015, doi: 10.1016/j.jcis.2015.04.014.
- [31] C. A. Quist-jensen, F. Macedonio, D. Horbez, and E. Drioli, “Reclamation of sodium sulfate from industrial wastewater by using membrane distillation and membrane crystallization,” *DES*, pp. 1–8, 2016, doi: 10.1016/j.desal.2016.05.007.
- [32] Y. Rasouli, M. Abbasi, and S. A. Hashemifard, “Oily wastewater treatment by adsorption-membrane filtration hybrid process using powdered activated carbon, natural zeolite powder and low cost ceramic membranes,” *Water Sci. Technol.*, vol. 76, no. 4, pp. 895–908, 2017, doi: 10.2166/wst.2017.247.
- [33] R. F. Darmayanti *et al.*, “Performance of modified hollow fiber membrane silver nanoparticles-zeolites Na–Y/PVDF composite used in membrane bioreactor for industrial wastewater treatment,” *Heliyon*, vol. 9, no. 11, p. e21350, 2023, doi: 10.1016/j.heliyon.2023.e21350.